

# ChemComm

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: P. K. Sukul, P. Bose, T. Takei, O. Yaghi, Y. He, M. Lee and K. Tashiro, *Chem. Commun.*, 2015, DOI: 10.1039/C5CC08973E.



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



ChemComm

COMMUNICATION

## A water-soluble metal–organic complex array as a multinuclear heterometallic peptide amphiphile that shows unconventional anion dependency in its self-assembly†

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x


www.rsc.org/

Pradip K. Sukul,<sup>a</sup> Purnandhu Bose,<sup>a</sup> Toshiaki Takei,<sup>a</sup> Omar M. Yaghi,<sup>a,b</sup> Ying He,<sup>c</sup> Myongsoo Lee<sup>c</sup> and Kentaro Tashiro\*<sup>a</sup>

**Water-soluble metal–organic complex array 1, bearing Ru(II), Pt(II) and Rh(III) complexes at the side residues of short peptide, exhibits anion and pH-responsive self-assembling behaviours in aqueous media. NaCl-induced aggregation of 1 at neutral pH was suppressed in phosphate buffered saline containing a mixture of Cl<sup>-</sup>, HPO<sub>4</sub><sup>2-</sup> and H<sub>2</sub>PO<sub>4</sub><sup>-</sup>, which is unconventional as a peptide amphiphile.**

Self-assembly of natural<sup>1</sup> as well as artificially designed<sup>2</sup> amphiphilic peptides is one of the most extensively studied subjects in peptide science, as it covers wide research areas from biomedical<sup>3</sup> to nano-electronics<sup>4</sup> fields. While there are increasing numbers of related studies with metallated peptide amphiphiles,<sup>5</sup> self-assembly of multinuclear heterometallic peptidic systems have been much less explored in spite of its potential utility for the controlled assembly of two or more different metal complexes into a particular arrangement.<sup>6</sup> Here we report a water-soluble metal–organic complex array (MOCA), a multimetallic peptidic array containing a predetermined sequence of metal centres, as a multinuclear heterometallic peptide amphiphile. Due to the presence of positively charged multiple metal complexes in its molecular structure, the water-soluble MOCA exhibited unconventional anion-dependency in its self-assembly, where, in contrast to most of pure organic peptide derivatives, its NaCl-induced aggregation is suppressed by the co-existence of more kosmotropic phosphate anions in phosphate buffered saline (PBS).

In 2011 we reported that sequential couplings of metallated amino acids on a polymeric resin successfully afforded MOCA containing up to six metal centres of three different metals arranged in a predetermined sequence.<sup>7</sup> Later, this approach was modularized to make larger MOCA whose molecular weights are close or even exceed those of small proteins.<sup>8</sup> As a MOCA possesses multiple metal complexes arranged in a specific unique sequence along the peptide backbone, it would be interesting to investigate its interactions with bio-related molecules such as peptides/proteins, nucleic acids and sugars having also a regulated

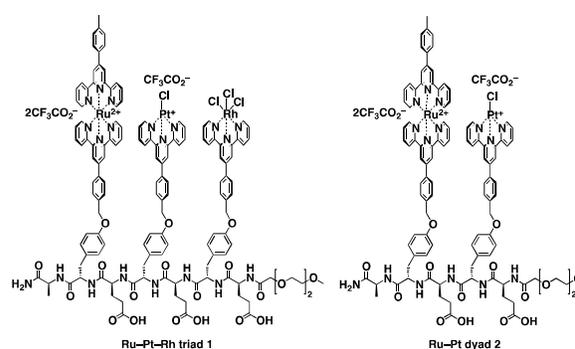

**Fig. 1** Molecular structures of water-soluble metal–organic complex array 1 and its reference 2.

sequence in their structure. Such an idea motivated us to synthesize the first water-soluble MOCA molecule. Here, we designed a heterometallic triad containing Ru(II), Pt(II) and Rh(III) ions as the first generation of water-soluble MOCA molecule (1 in Fig. 1). Metal complexes are chosen among the already successfully utilized in our previous works by considering the possible interactions with bio-related molecules such as DNA.<sup>9</sup> In addition to introduce cationically charged Ru and Pt complexes that are intrinsically water-soluble, we placed one glutamate (Glu) moiety to the every next of metallated amino acid moiety, and triethylene glycol (TEG) chain at the N-terminal of the array to give the

**Table 1** Self-assembling behaviours of 1 (50 μM) in aqueous media (10% CH<sub>3</sub>CN) in response to additives.


No.	Additives	pH	Morphology of the assembly
1	No	4.52	Not Detected
2	HCl (10 mM)	1.98	Spheres
3	NaCl (10 mM)	5.42	Amorphous aggregates
4	NaCl (100 mM)	5.34	Amorphous aggregates
5	NaOOCF <sub>3</sub> (100 mM)	5.41	Not Detected
6	NaCl/NaOOCF <sub>3</sub> (100/100 mM)	5.44	Not Detected
7	NaCl/KCl/Na <sub>2</sub> HPO <sub>4</sub> /KH <sub>2</sub> PO <sub>4</sub> (120/2.4/9/1.6 mM)	7.54	Spheres
8	NaCl/NaOH (100/0.0024 mM)	7.61	Amorphous aggregates

<sup>a</sup> International Center for Materials Nanoarchitectonics (WPI-MANA), National Institute for Materials Science, 1-1 Namiki, Tsukuba 305-0044, Japan. Fax: +81-29-860-4706; Tel: +81-29-860-4879; E-mail: TASHIRO.Kentaro@nims.go.jp

<sup>b</sup> Department of Chemistry, University of California–Berkeley, Materials Sciences Division, Lawrence Berkeley National Laboratory, and Kavli Energy NanoSciences Institute at Berkeley, University of California–Berkeley, Berkeley, California 94720, United States.

<sup>c</sup> College of Chemistry, Jilin University, Changchun 130-012, China.

† Electronic Supplementary Information (ESI) available: Synthesis of compounds 1 and 2 as well as characterisation of their self-assemblies. See DOI: 10.1039/x0xx00000x

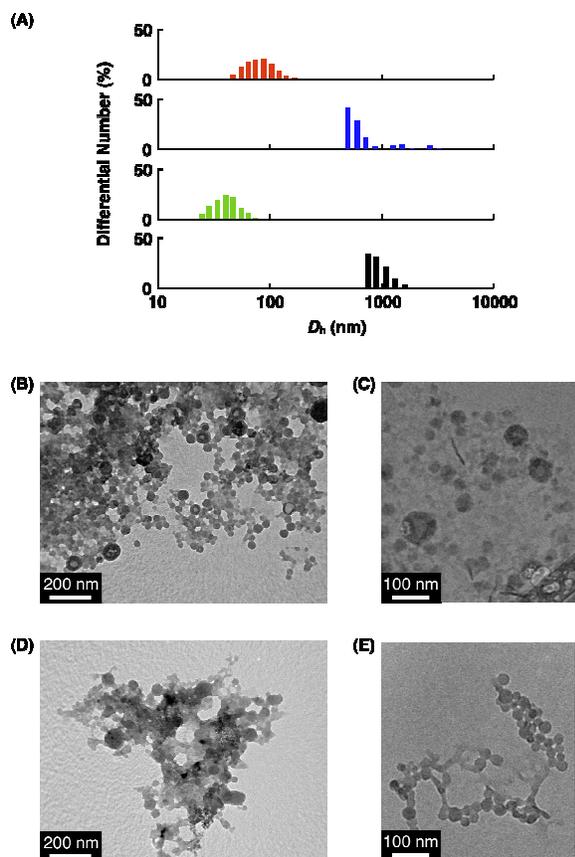

**Fig. 2** (A) DLS profiles of **1** under conditions 2 (red), 3 (blue), 7 (green) and 8 (black). (B, D) TEM and (C, E) cryogenic TEM images of non-stained **1** assembled in conditions 2 (B and C) and 7 (D and E).

molecule enough water-solubility (Fig. 1). Coupling of Ru monomer, Glu, Pt monomer, Glu, Rh monomer, Glu and TEG acid in this order and cleavage of the resultant species from the resin afforded a crude mixture containing **1**. Precipitation from DMSO by adding EtOAc and washing the resultant precipitate with MeOH gave analytically pure **1**, as confirmed by reverse-phase HPLC, in 8% overall yield.<sup>†</sup>

As-obtained Ru–Pt–Rh triad **1** was well soluble in DMSO and DMF while moderately soluble in MeOH and CH<sub>3</sub>CN. Dilution of its CH<sub>3</sub>CN solution with Milli-Q grade water (Table 1, condition 1) gave a transparent aqueous solution (10% CH<sub>3</sub>CN), in which no aggregation of the triad took place in its concentration range below 50 μM, as confirmed by dynamic light scattering (DLS) technique. While carboxylic acid moieties of **1** under this condition (pH = 4.52) exist as a mixture of CO<sub>2</sub>H and CO<sub>2</sub><sup>-</sup>, conversion of the latter into the former by lowering the pH value of the media down to 1.98 with HCl (Table 1, condition 2) made the solution gradually turbid. DLS analysis on the solution after standing for 2 days revealed that **1** aggregated into 50–200 nm sized objects (Fig. 2A red) over the concentration of 10 μM. Transmission electron microscopy (TEM) on a drop-cast sample revealed that these had a spherical morphology (Fig. 2B). Spheres larger than 70 nm tended to display images suggesting their hollow nature, which were hardly observed

in the case of smaller spheres. Cryogenic TEM on the same sample solution gave similar images (Fig. 2C), where the wall is estimated to have a thickness of 20–30 nm and be much bigger than the molecular size of **1**, as calculated from its CPK model to be no larger than 5 nm. These assemblies exhibited a positive Zeta potential ( $\zeta$ ) of 27.6 mV, possibly due to the presence of cationically charged Ru and Pt complexes in **1**. Absence of any clear CD patterns in the UV region between 200–250 nm (Fig. S10) suggests that **1** in those assemblies does not adopt a particular secondary structure such as  $\beta$ -sheet.

When an aqueous solution of **1** (10% CH<sub>3</sub>CN) was salted with NaCl (10 mM; Table 1, condition 3), the resultant solution again turned into non-transparent in 2 days at 37 °C to afford a suspension. In contrast to the case of acidification (Table 1, condition 2), however, NaCl-induced assembly of **1** gave only amorphous aggregates larger than 500 nm, as observed by DLS and TEM (Fig. 2A blue and S6A). Increase of NaCl concentration to one order of magnitude larger (100 mM; Table 1, condition 4) just slightly enlarged the size of aggregates (Fig. S6B and S8 red). As **1** intrinsically possesses trifluoroacetate as exchange-labile counter anions of its metal complex moieties (Fig. 1), we also tested sodium trifluoroacetate (NaOCOCF<sub>3</sub>, 100 mM; Table 1, condition 5) as a reference of NaCl, where no aggregate was detected by DLS. NaOCOCF<sub>3</sub> even repelled the effect of NaCl, as NaCl-induced aggregates of **1** apparently disappear in a few minutes by the post addition of NaOCOCF<sub>3</sub> (Table 1, condition 6) where a homogeneous solution without any DLS signals resulted after 3 h.

Being inspired by such anion sensitive self-assembly of **1**, we decided to investigate its behaviours in physiological conditions that generally contain complexed mixtures of anions. As a representative example, we chose PBS (Table 1, condition 7), one of the most commonly used buffer solutions in biological and biomedical researches. Although PBS contains more than 100 mM of NaCl, DLS profile of a PBS solution (10% CH<sub>3</sub>CN) of **1** displayed no light scatterings in μm-scale region but those only at below 100 nm (Fig. 2A green). Suppression of the NaCl-induced aggregation of **1** in PBS is not due to the increase of pH value of the media up to 7.54, as the salting-out effect of NaCl on **1** was preserved at pH of 7.61 (Table 1, condition 8; Fig. 2A black and S6C). TEM as well as cryogenic TEM observations on the PBS solution of **1** (Fig. 2D and E) visualized spheres whose sizes are less than 100 nm. As is the case of spheres obtained under condition 2, those in PBS were positively charged ( $\zeta$  = 22.2 mV). The observed small salting-out effect of PBS on **1**, less significant than that of NaCl under the same pH condition (condition 8), is unique for self-assembly of peptide amphiphiles as generally kosmotropic anions such as HPO<sub>4</sub><sup>2-</sup> and H<sub>2</sub>PO<sub>4</sub><sup>-</sup> in the Hofmeister series<sup>10</sup> promote assemblies of peptides and proteins more efficiently than Cl<sup>-</sup>.<sup>11</sup> This is possibly due to the fact that the molecular structure of **1** contains multiple cationic moieties such as doubly charged Ru and singly charged Pt metal complexes, whose interactions with anions could play the decisive role to control the self-assembling behaviours of **1**.<sup>12</sup> On the other hand, presence of the water-insoluble, charge neutral Rh-complex moiety in the molecular structure of **1** is also responsible for its spherical assembly formation in PBS, as reference Ru–Pt dyad **2** (Fig. 1) did not form any assemblies detectable by DLS under the same condition even **2** as well as **1** aggregated heavily under condition 8

(Fig. S9 and 2A black, respectively). In relation to this, presence of hydrophobic Nile red dye (1  $\mu\text{M}$ ) of only 2 mol% with respect to **1**, promoted the aggregation of **1** (Fig. S8 blue), suggesting that the self-assembly of **1** in PBS is sensitive to the subtle change of the balance between hydrophobic and ionic interactions of **1**. It would be also noteworthy that the Ru–Pt–Rh sequence in **1** can produce a gradient of cationic charge upon dissociation of non-coordinating trifluoroacetate anions (Fig. 1).

In summary, we have reported **1** as the first example of water-soluble MOCA and investigated its self-assembling behaviours in aqueous media. Unconventional anion-dependency of its self-assembly as a peptide amphiphile recommends us to be more conscious of a less considered effect of metallated peptide structures, which is particularly meaningful under physiological conditions where competitive interactions with co-existing anions play a fundamental role. Spherical assemblies of **1** were also observed in an aqueous cell culture medium (Dulbecco's modified Eagle's medium) (10% DMSO) containing fetal bovine serum (Fig. S7 and S8 green), suggesting future potential utility of water-soluble MOCA in biomedical area. Considering also the observed phosphate-responsive self-assembling behaviours of **1**, its hybridization with nucleic acids for delivery is a one of the future research subjects worthy to try.

This work was partially supported by the World Premier International Research Center (WPI) Initiative on Materials Nanoarchitectonics and a Grant-in-Aid for Challenging Exploratory Research (No. 26620139) from MEXT, Japan.

## Notes and references

- (a) W. Colon and J. W. Kelly, *Biochemistry*, 1992, **31**, 8654–8669; (b) K. A. Conway, J. D. Harper and P. T. Lansbury, Jr., *Biochemistry*, 2000, **39**, 2552–2563; (c) C. P. Jaronec, C. E. MacPhee, V. S. Bajaj, M. T. McMahon, C. M. Dobson and R. G. Griffin, *Proc. Natl. Acad. Sci. U.S.A.* 2004, **101**, 711–716; (d) I. W. Hamley, *Chem. Rev.*, 2012, **112**, 5147–5192.
- (a) K. Yamada, H. Ihara, T. Ide and T. Fukumoto, *Chem. Lett.* 1984, 1713–1716; (b) J. D. Hartgerink, E. Beniash and S. I. Stupp, *Science*, 2001, **294**, 1684–1688; (c) D. W. P. M. Löwik and J. C. M. van Hest, *Chem. Soc. Rev.*, 2004, **33**, 234–245; (d) E. Gazit, *Chem. Soc. Rev.*, 2007, **36**, 1263–1269; (e) I. W. Hamley, *Soft Matter*, 2011, **7**, 4122–4138; (f) S. Fleming and R. V. Ulijn, *Chem. Soc. Rev.*, 2014, **43**, 8150–8177.
- (a) G. A. Silva, C. Czeisler, K. L. Niece, E. Beniash, D. A. Harrington, J. A. Kessler and S. I. Stupp, *Science*, 2004, **303**, 1352–1355; (b) E. Kokkoli, A. Mardilovich, A. Wedekind, E. L. Rexeis, A. Garg and J. A. Craig, *Soft Matter*, 2006, **2**, 1015–1024; (c) X. Zhao, F. Pan, H. Xu, M. Yaseen, H. Shan, C. A. E. Hauser, S. Zhang and J. R. Lu, *Chem. Soc. Rev.*, 2010, **39**, 3480–3498; (d) K. H. Smith, E. T.-Montes, M. Poch and A. Mata, *Chem. Soc. Rev.*, 2011, **40**, 4563–4577; (e) H. Hosseinkhani, P.-D. Hong and D.-S. Yu, *Chem. Rev.*, 2013, **113**, 4837–4861.
- (a) M. Reches and E. Gazit, *Science*, 2003, **300**, 625–627; (b) H. Shao, T. Nguyen, N. C. Romano, D. A. Modarelli and J. R. Parquette, *J. Am. Chem. Soc.*, 2009, **131**, 16374–16376; (c) L. A.-Abramovich and E. Gazit, *Chem. Soc. Rev.*, 2014, **43**, 6881–6893.
- Selected recent examples containing metal complexes in the structure; (a) T. Sawada, A. Matsumoto and M. Fujita, *Angew. Chem. Int. Ed.*, 2014, **53**, 7228–7232; (b) Y. Zhang, N. Zhou, J. Shi, S. S. Pochapsky, T. C. Pochapsky, B. Zhang, X. Zhang and B. Xu, *Nature Commun.*, 2015, **6**, 6125; (c) B. Kemper, Y. R. Hristova, S. Tacke, L. Stegemann, L. S. van Bezouwen, M. C. A. Stuart, J. Klingauf, C. A. Strassert and P. Besenius, *Chem. Commun.*, 2015, **51**, 5253–5256; (d) R. Zou, Q. Wang, J. Wu, C. Schmuck and H. Tian, *Chem. Soc. Rev.*, 2015, **44**, 5200–5219.
- (a) A. M. Fracaroli, K. Tashiro and O. M. Yaghi, *Inorg. Chem.*, 2012, **51**, 6437–6439; (b) K. Isozaki, Y. Haga, K. Ogata, T. Naota and H. Takaya, *Dalton Trans.*, 2013, **42**, 15953–15966.
- P. Vairaprakash, H. Ueki, K. Tashiro and O. M. Yaghi, *J. Am. Chem. Soc.*, 2011, **133**, 759–761.
- K. V. Sajna, A. M. Fracaroli, O. M. Yaghi and K. Tashiro, *Inorg. Chem.*, 2015, **54**, 1197–1199.
- K. van der Schilden, F. Garcia, H. Kooijman, A. L. Spek, J. G. Haasnoot and J. Reedijk, *Angew. Chem. Int. Ed.*, 2004, **43**, 5668–5670.
- (a) F. Hofmeister, *Arch. Exp. Pathol. Pharmacol.*, 1888, **24**, 247–260; (b) Y. Zhang and P. S. Cremer, *Annu. Rev. Phys. Chem.*, 2010, **61**, 63–83; (c) P. Lo Nostro and B. W. Ninham, *Chem. Rev.*, 2012, **112**, 2286–2322.
- (a) T. B. Schuster, D. de B. Ouboter, E. Bordignon, G. Jeschke and W. Meier, *Soft Matter*, 2010, **6**, 5596–5604; (b) M. Cao, Y. Wang, X. Ge, C. Cao, J. Wang, H. Xu, D. Xia, X. Zhao and J. R. Lu, *J. Phys. Chem. B*, 2011, **115**, 11862–11871; (c) E. K. Wilson, *Chem. Eng. News*, 2012, **90**, July 16, 42–43; (d) S. Roy, N. Javid, P. W. J. M. Frederix, D. A. Lamprou, A. J. Urquhart, N. T. Hunt, P. J. Halling and R. V. Ulijn, *Chem. Eur. J.*, 2012, **18**, 11723–11731.
- Reversal of the Hofmeister series for anions due to the electrostatic interaction with cationic charges on the peptides have been discussed in J. Paterová, K. B. Rembert, J. Heyda, Y. Kurra, H. I. Okur, W. R. Liu, C. Hilty, P. S. Cremer and P. Jungwirth, *J. Phys. Chem. B*, 2013, **117**, 8150–8158.